



Research
Hydraulic Engineering—Review

Emerging and Innovative Materials for Hydropower Engineering Applications: Turbines, Bearings, Sealing, Dams and Waterways, and Ocean Power



Emanuele Quaranta^{a,*}, Peter Davies^b

^a European Commission Joint Research Centre, Ispra 21027, Italy

^b Marine Structures Laboratory, IFREMER Centre Bretagne, Plouzané 29280, France

ARTICLE INFO

Article history:

Received 28 October 2020

Revised 7 April 2021

Accepted 25 June 2021

Available online 15 September 2021

Keywords:

Bearing

Composite

Dam

Hydropower

Material

Ocean

Seal

Turbine

ABSTRACT

The hydropower sector is currently experiencing several technological developments. New technologies and practices are emerging to make hydropower more flexible and more sustainable. Novel materials have also been recently developed to increase performance, durability, and reliability; however, no systematic discussions can be found in the literature. Therefore, in this paper, novel materials for hydropower applications are presented, and their performance, advantages, and limitations are discussed. For example, composites can reduce the weight of steel equipment by 50% to 80%, polymers and super-hydrophobic materials can reduce head losses by 4% to 20%, and novel bearing materials can reduce bearing wear by 6%. These improvements determine higher efficiencies, longer life span, waste reduction, and maintenance needs, although the initial cost of some materials is not yet competitive with respect to the costs of traditional materials. The novel materials are described here based on the following categories: novel materials for turbines, dams and waterways, bearings, seals, and ocean hydropower.

© 2021 THE AUTHORS. Published by Elsevier LTD on behalf of Chinese Academy of Engineering and Higher Education Press Limited Company. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

1. Introduction

Hydropower is a renewable energy source that converts the power of water into electricity through the rotation of a turbine and an electric generator. The global installed hydropower capacity in 2020 was 1308 GW, and it is expected to grow by approximately 60% by 2050 to limit the rise of the global temperature primarily caused by fossil fuels and to satisfy the energy demand. Hydropower growth would help generate 600 000 specialized jobs and would require an estimated investment of 1.7 trillion USD [1].

The hydropower sector is affected by new challenges: ① Flexibility is required to compensate for the highly variable generation of wind and solar power and to provide ancillary services, both at the daily and seasonal scales, working efficiently under off-design conditions. Pumped hydropower plants are essential to provide and consume energy on demand. ② Larger storage reservoirs are required to mitigate floods and droughts. ③ Rural electrification

is also stimulating small-scale hydropower plants by powering existing hydraulic structures and small barriers, which are already serving other purposes. ④ Impacts generated by hydropower plants need to be minimized, and hydropower needs to be eco-friendly. Therefore, several emerging hydropower technologies are underway to meet these needs [2–6]. Novel materials can play an important role in the decrease of manufacturing labor costs, pollution, waste, and material (especially owing to the substantial weight reduction of hydro components, such as turbine runners), while improving performance and durability. However, the initial cost of some novel materials is not yet competitive owing to the high fabrication and raw material costs.

However, despite the relevance of this topic, an up-to-date scientific review of novel materials for hydropower applications has not been reported in the literature. For example, only very few reports on the development or use of composite materials in hydropower turbines have been published to date, and the few published reports are limited to either theoretical studies or very specific applications [7]. Therefore, in this document, novel materials for hydropower applications are discussed, especially those that have been introduced recently, that is, in the last decades,

* Corresponding author.

E-mail addresses: emanuele.quaranta@ec.europa.eu, quarantaemanuele@yahoo.it (E. Quaranta).

with some related case studies. This review is not conceived to describe and analyze traditional materials for hydropower applications, for which ad hoc references can be found in the literature.

Novel materials are categorized into the following categories: novel materials for turbines, dams and waterways, bearings, seals, and ocean hydropower. A section is provided to discuss the limitations and future perspectives.

2. Novel materials for turbines and hydraulic equipment

The turbine is the component that converts the power of water into mechanical power. A turbine is made of blades that rotate around the rotation axis when interacting with water flow. Hydraulic turbines can be classified into reaction turbines, which mainly exploit the pressure of water, and action turbines, which exploit the flow velocity, that is, the kinetic energy of water and its flow momentum. Gravity machines exploit the weight of water and are only used for very low-head applications (< 5 m) [8]. Hydrokinetic turbines exploit the kinetic energy of rivers, similar to wind turbines.

The materials commonly used for high-head turbines are austenitic steel alloys with chromium content of 17% to 20% (> 12%; the minimum chromium composition should be 12% to provide atmospheric corrosion resistance), to improve the stability of the protective film and a longer life span of the runner blades. Alternatively, the blades can be made of martensitic stainless steel, whose strength is twice that of austenitic stainless steel [9]. Low-head machines are generally made of stainless steel or Corten steel [10]. Hydrokinetic turbines are generally made of fiber glass, carbon fiber (CF), or reinforced plastics [11].

Generally, the turbines employed for high-head applications must be made with materials capable of resisting both the high stresses generated by the water pressure and fatigue, erosion, and cavitation. Low-head turbines do not experience high stresses and pressures; however, the power/weight ratio is quite small. Therefore, the principal aim of the chosen materials is to reduce their weight[†] and resist abrasion and fatigue. Furthermore, a large turbine weight can significantly increase transportation and installation costs, especially in remote areas. Thus, it is important to reduce the weight of the turbine to make very low-head applications more economically viable [7]. For example, in Ref. [12], the efficiency of a laboratory-scale vortex turbine increased from 33.6% to 34.8%, whereas the weight reduced from 15 to 6 kg passing from steel to aluminum. An additional benefit of weight reduction is the possibility of easing the transport and installation procedure, especially in offshore and mountainous locations.

As mentioned above, novel materials can also ensure a longer life span of hydro equipment by limiting the effects of cavitation, erosion, corrosion, and fatigue [13–16]. Cavitation occurs owing to the formation of voids and bubbles, where the pressure of the liquid changes rapidly. The implosion of such voids can cause strong shockwaves resulting from the change in fluid pressure, especially in reaction turbines. Silt erosion damages components by the collision of particles on the material. Fatigue is the process of repeated cyclic stresses, for example, during load variations and vibrations. The hydropower industry is also affected by biofouling (the growth of invasive species such as zebra mussels on turbines and other structures from accumulated bacteria). Corrosion is the combined effect of oxygen and air, and it can be minimized using novel materials instead of steel. Stainless steels are complex alloys containing primarily Cr and Ni and other minor elements such as

Mo, Mn, C, N, and Ti. Based on their solubility, these elements can precipitate as of secondary particles, such as sulfides, carbides, and nitrides, improving the mechanical properties and corrosion resistance of the installed components [11].

Recently, novel materials have been introduced: ① coating layers to better resist erosion, corrosion, and cavitation, and to reduce friction (i.e., related head losses), and ② structural materials to better resist loads and reduce weight [7]. Novel fabrication techniques, such as three-dimensional (3D) printing [17][‡] and surface treatments [15], are also being developed.

2.1. Novel coating materials

Superhydrophobic coating materials offer great opportunities to reduce surface friction [14,18,19]. Their application was numerically tested for a very low-head turbine [20], increasing the turbine efficiency by 4% at the design point (Fig. 1 [20]). Furthermore, superhydrophobic materials are self-cleaning, resistant to corrosion, and anti-icing [20,21]. Similarly, the superhydrophobic lubricant fused composite prevents mussels from attaching to hydropower structures. It was developed in support of the Water Power Technologies Office, USA, and partnership with the US Bureau of Reclamation, US Army Corps of Engineers, and BioBlend Renewable Resources, USA [22].

Coatings are also important for resisting cavitation and abrasion (especially in waters with high sediment loads). Coatings can be mainly classified into hard layers of oxides, carbides, and nitrides, soft non-metallic layers (polyurethane, epoxy, and nylon), and composite cermet coatings of hard reinforcements in tough matrix materials [15].

In Ref. [23], a review of novel coating materials for hydro turbines was conducted. Bimodal coatings with both nanometric and micrometric tungsten carbide (WC) grains, for example, WC–10Co–4Cr bimodal coatings on 35CrMo, have a better microstructure, lower porosity, higher hardness, and higher resistance to slurry erosion compared to nano- and conventional coatings. Moreover, the bimodal structure exhibited maximum resistance to slurry erosion.

In Ref. [13], novel coatings for turbines have been proposed. The use of a refinement layer of 13Cr4Ni steel for refinement led to a 2.6 times improvement in microhardness. The Ni–Al₂O₃ based composite coatings with 60 wt% alumina exhibited the highest microhardness and reduced erosion. High-velocity oxygen fuel (HVOF)-coated steel provides better erosion resistance than plasma nitride 12Cr and 13Cr–4Ni steels. HVOF sprayed tungsten carbide coating instead, in Ref. [24]. Plasma nitriding was found to be an excellent surface treatment to prevent wear in hydraulic turbines. It reduced the erosion rate by 96% under cavitation erosion and jet slurry erosion by 51%, whereas HVOF coating decreased the jet slurry erosion rate by up to 46%, with poor results under cavitation erosion [24]. More research should be focused on better characterization of these materials under different operations.

In Ref. [15] it has been reported that materials with altered grain size, phase content, or varied mechanical properties generate different cavitation erosion resistances; thus, advanced surface treatment techniques are under investigation, for example, friction stir processing.

Triboelectric materials that generate electricity from small-scale mechanical contacts are also under development [25]. For example, a novel organic coating triboelectric nanogenerator has been fabricated using acrylate resin (with the addition of

[†] The power generated by a turbine is proportional to the product of the head and flow, thus turbines installed in low head sites need high flow rates to generate significant power, and thus require a large runner diameter. Further considerations on this can be found in Ref. [10] for water wheels, Kaplan and Francis turbines.

[‡] It is worth mentioning that a type of 3D printing in turbine manufacturing exists since the 1990s when the "MicroGuss" by Sulzer (now Andritz) was developed. With this method, a Pelton turbine is sprayed by micro-welding which gives much higher resistances than forging from one piece.

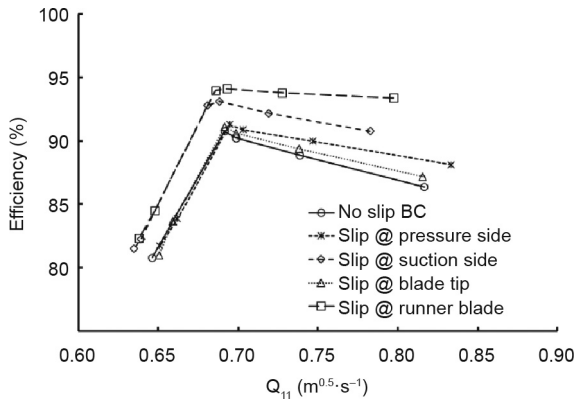


Fig. 1. Hydraulic efficiency versus unit discharge Q_{11} is shown under different wall boundary conditions (BCs). Different cases are: no-slip for the entire runner, slip (i.e., superhydrophobic material) for pressure side, slip for suction side, slip for blade tip, and slip for the entire blade surface [20].

fluorine-containing materials) as the friction layer material to improve the deficit of existing liquid–solid triboelectrification technologies (high cost, complexity, and microstructures that can be easily damaged). This coating was used to power several commercial light emitting diodes (LEDs) on a ship by collecting the wave energy during the voyage, with good output performance and stability, simple process, and low cost [26,27]. Future applications in ocean hydropower technologies and in water wheels may be developed [28].

2.2. Novel structural materials: Composite materials

Composites have been the primary material for large wind turbine blades owing to their stiffness, high specific strength, and reasonable cost. However, they have not been extensively applied to hydropower turbines owing to the lack of research in this area. Composite materials can reduce the weight of turbine components by up to 80%. Stainless steel has a density ranging from 7500 to 8000 $kg.m^{-3}$, whereas the composite material density generally ranges from 1500 $kg.m^{-3}$ (e.g., CF-reinforced polymers) to 2500 $kg.m^{-3}$ (e.g., glass fiber (GF), reinforced polymers) [7].

Composite materials could provide new opportunities in the hydropower sector owing to their excellent properties such as low density, high stiffness, toughness, and good fatigue behavior. Furthermore, they are resistant to corrosion and abrasion, easy to assemble, resistant to chemical agents, and can increase the life of turbine blades while minimizing maintenance costs. However, composite materials often have higher deformability, which could be a problem for high-speed rotation machines for joint and gap safety in the casing [29].

Composite materials are composed of a mixture of micro- or macro-constituents that differ in form and chemical composition and are essentially insoluble in each other, to improve material properties such as stiffness, strength, and toughness. The constituents retain their identities in the composite; thus, they do not dissolve or merge completely in each other, although they act together. Normally, the components can be physically identified and exhibit a distinct interface between one another [30]. Fiber-reinforced composites are often developed to improve the strength-to-weight and stiffness-to-weight ratios (i.e., to produce lightweight structures that are both strong and stiff). Fibers are available in three basic forms.

- Continuous fibers: long, straight, and generally used parallel to each other in unidirectional layers.
- Multi-directional continuous fibers: woven fabric or stitched layers, providing multidirectional strength with orientations adapted to the loading conditions.

- Chopped fibers: short and generally randomly distributed (generally fiber glass).

Three main reinforcing fiber materials are available for composite materials: glass, carbon, and aramid (Kevlar™), which are typically combined with a polymer matrix. CF composites are lightweight, stiffer, stronger, and more expensive than glass. They are extensively used in aircraft structures and wind turbine blades, which are often very long (100 m) [15,31,32]. Both carbon and GF composites do not require expensive corrosion protection because they do not corrode and degrade like steel; however, they can undergo wet aging [33–35]. Aramid fibers such as Kevlar™ are often added as composite reinforcements to provide impact resistance [36]. However, fiber-reinforced polymers are mainly limited to applications in turbines with low rotational speeds (e.g., in ocean applications and low-head turbines), because brittle failure may occur at high rotational speeds, which could have catastrophic consequences.

The study of composite materials has been one of the major objectives of computational mechanics research in the last decade. Numerical simulations of orthotropic composite materials have been performed based on the average properties of their constituents; however, few models can work beyond the constituent elastic limit state. Thus, most procedures are limited to the numerical computation of elastic cases. Different theories have been proposed to solve this problem by considering the internal configuration of the composite to predict its behavior. The two most common theories are homogenization and mixing theories [37]. These two theories were implemented in Ref. [37] to study a hydrokinetic turbine, and it was found that runners made with composites have 5.5 times lower starting torque than the steel rotor, better performance at low water velocities, and are easier to transport, handle, repair, and start.

Some interesting examples where composite materials have been applied in high-head turbines can be found in Refs. [7,30,38,39]. In Ref. [30], a Pelton turbine with 22 buckets was made using Kevlar™ 49 and chopped GFs as reinforcing fibers in an epoxy matrix. Their manufacturing process has been described, although the turbine has not been tested in terms of efficiency and lifespan. In Ref. [39] the buckets of a Pelton turbine were produced from a composite material (carbon + thermoplastic) using a 3D printer, 1/8 lighter than the steel material, and with similar strength. The material cost of the Pelton composite bucket composite was 200 EUR, whereas the unit cost of the metal bucket was 300 EUR. In Ref. [7], the authors investigated the potential of replacing stainless steel blades of a small propeller-type turbine with lightweight composite blades. A CF-reinforced thermoplastic was selected because of its lower density and smaller blade tip displacement, exhibiting the same peak efficiency as that achieved by the stainless-steel turbine. However, the composite blades were subject to a slightly higher degree of blade bending, increasing the hydraulic head. In Ref. [38], a feasibility study on 2 MW Francis turbines revealed that a composite turbine could weigh lesser by 50% to 70% than current steel versions. The weight reduction is depicted in Fig. 2, when the penstock, spiral case, guide vanes, turbine runner, and draft tube are considered.

Gravity machines are also experiencing novel material developments. Carbon steel has been used for the overshot water wheel in Judenburg, Austria [40] for a 4 m head application (Fig. 3). The use of carbon steel allowed a lighter wheel to be built, whose weight of 7 kN was lower than the expected steel of 9.8 kN (estimated by applying Eq. (1)) [10].

$$G = g\rho_s\varphi[H(Q+k)]^\psi \quad (1)$$

where G (kN) is the weight of an overshot water wheel made of steel, H is the head (m), Q is the flow rate ($m^3.s^{-1}$),

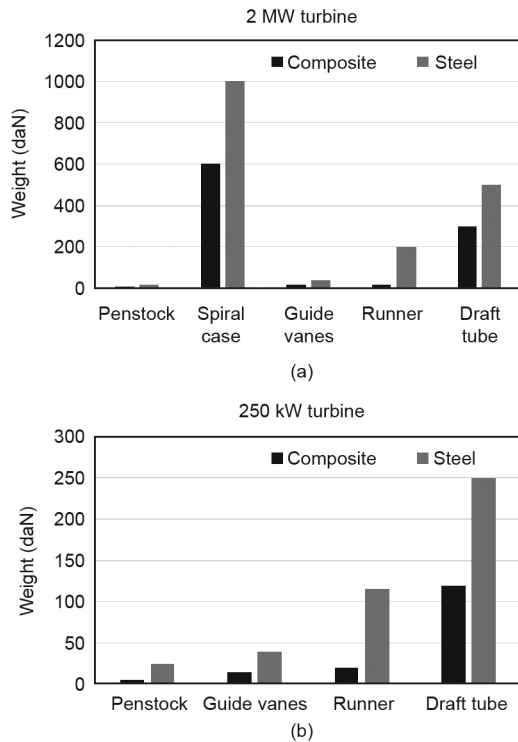


Fig. 2. Two study cases where the weight of components is compared between composite and steel materials (adapted from Ref. [38]): (a) 2 MW turbine and (b) 250 kW turbine. 1 daN = 10 N.



Fig. 3. Overshot water wheel, 4 m in diameter and 0.75 m wide.

$k = 0.15$, $\varphi = 0.151$, and $\psi = 2.042$ are empirical coefficients for the overshot wheel, and ρ_s is the material (steel) density.

High-density polyethylene (HDPE) is another material recently introduced in the low-head hydro sector. It is lighter than steel and has been used in water wheels. It is comparatively cheaper and more resistant to non-corrosive water (ocean water is an example of corrosive water). Furthermore, on-site water wheel disassembly and reassembly are easier because of the lightweight of the HDPE components [41,42].

In July 2019, Percheron Power, with support from Pacific Northwest National Laboratory (PNNL) and Utah State University's Water Research Lab, USA, designed and tested an Archimedes screw made of composite materials and leveraging advanced manufacturing methods. It was found that light resin transfer molding exhibited lower production costs, lower waste, and emissions, and resulted in a weight lower by 25% to 30% than steel. Because the composite blades were gel-coated while in the mold, they required no primer or corrosion-resistant paints, and the cor-

rosion and friction were reduced, minimizing friction head losses [43].

Also the ocean hydropower technology is included within the low-head context, and composite materials are used. For example, the first tidal turbine prototype, the SeaGen tidal turbine (1.2 MW of installed power in Northern Ireland [31,44]), comprises a combination of GF and CF in a polymer matrix. The benefits were low weight and high stiffness, an effective strength-to-weight ratio, and economies of scale for complex shape manufacturing. However, the corrosion of ocean water may be a problem. Further details can be observed in the ocean hydropower section below.

3. Novel materials for dams and hydraulic structures

A dam is a hydraulic structure that intercepts the water flow of the river and generates an artificial basin upstream. When a dam is built to regulate the upstream water level of a river, without generating an appropriate artificial basin to store a significant amount of water, it is called a weir or barrier. Reservoirs are multipurpose infrastructures that are effective for flood control, irrigation, power generation, and water supply. Dam safety has improved significantly, especially since the 1990s. However, dam engineers continue to seek novel technologies to build dams that are safer, more economical, and more eco-friendly. A review of dams and their common materials can be found in Refs. [45,46]: Arch dams are typically constructed today of mass concrete, with a relatively low cement content, whereas gravity dams are made of loose material. Dams built of loose material are called embankment dams and, in particular, earth dams or rockfill dams. As a tight element in addition to clay-silt cores, gravity dams may also have an upstream face element either of concrete (called concrete-faced rockfill dam) or a bituminous layer or even geo-membranes [46].

Recently, novel dam materials have been introduced. For appurtenant dam structures, GF-reinforced concrete is a cement-based composite with alkali-resistant GFs that are randomly dispersed throughout the product. This can be used as surface protection, for example, on spillway structures in addition to other concrete composites, having high resistance against abrasion and cavitation. The fibers support the tensile stress similarly to the steel in reinforced concrete, increasing the lifespan of the structure. The addition of conductive CFs to a precast concrete structure enables the material to provide real-time load information on the structure, thus allowing the identification of problems before stress or cracking becomes visible to the human eye [47].

Another innovation is the rock-bolted underpinning system [48]. A Global Positioning System (GPS)-guided, rock-bolted underpinning system provides a linkage to the riverbed. This leads to easier installation and fastening of the structure. Each segment is secured to the riverbed or an existing dam using multiple rock bolts, each of which can sustain large loads. Although metallic rock bolts have been used in mining for many years, they have also been applied in dams [49,50]. In some applications, pultruded composite rock bolts may also be significant, and their light weights can reduce the environmental impact [51].

Rock-filled concrete dams are built by placing very large rock boulders from quarries in layers and then filling the voids with high fluidity and self-compacting concrete that can fill the voids easily [52]. In addition to the limitation of the thermal effects and cracking risk of concrete during construction, the advantages of rock-filled concrete include the reduction of cement/concrete quantity and the lack of need to compact the concrete. The challenge is to find adequate self-compacting concrete with high viscosity and sufficient strength. This method is an alternative to roller-compacted concrete, where dry concrete with low cement content is placed in small layers and then compacted with

vibrating rollers such as soil compaction. Rock-filled concrete dams have the advantage of being overtopped without failure risk during extreme floods, and also, during construction. Thus, river diversion structures, such as diversion tunnels, can be limited. The cemented rockfill has a greater deformation modulus than the traditional rockfill material, reducing the probability of large deformation in rockfill dams, with economic benefits, and therefore limiting thermal effects during construction [53]. The concept of the cemented material dam was proposed in 2009: 10% to 20% of the cost could be saved, and the construction period could be significantly reduced. The preparation of the cemented material involves less processing, screening, grading, and mixing than concrete. The roller compacted concrete method is a recent method for building concrete dams, which has been optimized over the last decades, for example, based on the novel concept of the faced symmetrical hardfill dam and trapezoidal cemented sand–gravel dam [54]. Compared to roller compacted concrete, which uses selected cement–sand–gravel mixtures as traditional concrete, the concrete-face rockfill dams and cemented soil dams add cement to an almost untreated soil material. The lower resistance was compensated by the symmetrical or trapezoidal profiles.

The bituminous conglomerate is another trend that is being developed to cover dam surfaces [55]. Modified bitumen sealing membrane (MBSM) comprises a composite of modified bitumen and aggregates. The waterproofing action is performed by the binder stratifications of the modified bitumen sealing membrane, which are comparable to a layer of 3 cm thick in bituminous conglomerate from the resistance viewpoint to mechanical impacts [56]. However, bituminous material is limited to a certain height of a dam because the layers transform to plastic under a certain self-weight, and care should be devoted to the horizontal joint on the dam crest, that should be eventually reinforced to avoid that the layers slide downward generating creeks and infiltrations.

An important theme is the development of concrete and injection advanced technology using chemical adjuvants aim at tightening, self-compaction, viscosity reduction, improved thermal behavior, flexibility, fast placing, and crack healing. Significant progress has been made in this area over the last few decades [52].

The development of inflatable rubber weirs is also underway, especially for small hydropower sectors and head applications below 3 m. The inflatable weirs are flexible elliptical structures made of rubberized material attached to a rigid concrete base and inflated using air, water, or a combination of both. When the structure is inflated, it acts as a weir, and it can be deflated when flushing of sediments is needed. The cost is generally lower than that of common weirs of the same size [57]. Steel clapping plates were used to connect rubber bodies. However, they may corrode, and investigations of GF-reinforced polymer composites are underway to replace steel [58].

Innovative coatings and surface treatments of hydraulic structures and waterways are also under investigation. Novel coatings for waterways (e.g., penstocks) reduce surface friction and consequently increase electricity generation. A detailed review of both traditional and innovative materials [59] was published in 2016, and the key points are summarized here. The coating of concrete-lined tunnels with epoxy-based paints may reduce friction losses and prevent future degradation while lining with steel or with polyethylene reinforced by fiberglass is commonly implemented. However, although newer liners have longer lifetimes and limited maintenance, the cost of lining 1 m of the tunnel is often twice to thrice that of its excavation. Some coating materials described in Ref. [59], with related case studies, are: ① polymer-modified cement-based mortar for a 12 km-long horseshoe section tunnel with an average diameter of 9.45 m, reducing the head loss by 20% and with a cost of 30 USD·m⁻²; ② a latex-based primer and topcoat and an epoxy primer with added solids applied after clean-

ing, generating a power increase of 11%; ③ superhydrophobic materials with a related drag reduction of up to 30% and superhydrophilic surface (drag reduction by water–water interface) with drag reduction of up to 5%. These measures are of particular interest in refurbishment projects.

An additional example of a novel material for penstocks is described in Ref. [60], where steel of high tensile strength (950 N·mm⁻²) was used in the Kannagawa plant to reduce costs. However, brittle failures may arise, and welding is critical for the inclusion of micro-fissures. This has been extensively described in Ref. [61]. Probabilistic design methods have to be used for such high-strength steel considering imperfections in the material, especially welding.

4. Novel materials for bearings

Bearings are critical components of the hydraulic turbine units, used in supporting rotating components while minimizing friction (i.e., the need for grease) and keeping the shaft of the components aligned. The operation of hydropower turbine bearings is challenging owing to the extreme contact pressure conditions (over ~30 MPa) over a lifespan of 40 years [62]. Hydrodynamic sliding bearings are the most used and can be classified into three major categories: journal bearings, thrust bearings, and shaft bushings [62,63].

Friction and wear are the major factors in maintenance problems and costs. Therefore, most turbines use pressurized oil to lubricate the turbine bearings to reduce friction, wear, maintenance interventions, and costs, and to improve machine performance. However, oil leakage from hydraulic turbines may have negative impacts on the environment and some operational and maintenance problems [64]. Hence, the use of eco-friendly tribological components/technologies (e.g., bearings), known as eco-tribology, is considered as an effective engineering practice to improve the sustainability of hydropower applications [65].

To eliminate the possible danger of oil spillage from hydropower units, the concept of eco-tribology in the hydropower sector has undergone rapid development in recent years, especially in the bearing context. Water-based lubricants, ecological/vegetable lubricants, and self-lubricant bearings (with tribo-materials), with improved or similar tribological performance with respect to the traditional ones, have been developed.

Vegetable/ecological oils are biodegradable; however, they have the disadvantage of breaking down more quickly than other mineral oils when mixed with water, which affects their mechanical properties. Furthermore, they are more expensive than mineral oil, and some seal materials are susceptible to damage when exposed to vegetable oils [66]. In Ref. [67], an industrial case study is described, whereas in Ref. [66], the experience of hydropower companies with vegetable oils has been discussed.

Bearings lubricated with water operate in a boundary or mixed lubrication regime for relatively longer periods because of the low viscosity of water, especially when the low sliding speeds and start/stop cycles are considered [68]. Ingram and Ray [69] stated that water-lubricated guide bearings both contribute to increasing the overall plant efficiency by reducing friction losses and maintenance compared to oil-lubricated ones, owing to their low cost, nontoxicity, and high heat capacity. Oguma et al. [70] described the performance of a water-lubricated guide bearing that was specifically designed for a multi-nozzle vertical Pelton turbine. However, water is a poor lubricant for severe engineering applications due to its low viscosity, solvent nature (corrosiveness), and high volatility [62]. The low viscosity can significantly increase friction and shorten the effective wear life of the bearings. Therefore, the use of water-based lubrication introduces new

engineering challenges, especially the material choice for bearing surfaces that can ensure a friction coefficient below 0.1, and a lifetime of 40 years [68].

Self-lubricating bearings have been introduced to avoid the use of lubricants. They are generally made of bronze (metal-based) or Teflon (plastic-based) [63,71]. With regard to turbines, composite materials and self-lubricating polymers are also used as thrust bearings for runners, wear plates, and trunnion bearings on spillway gates. Diamond-like carbon coating technology has also developed significantly in the last decade [65]. However, owing to the widespread of intermittent wind and solar power plants with unpredictable output, the operating conditions of hydropower plants are becoming more variable in response to the grid requirements, and self-lubricating bearings used in controlling the turbine blades and guide vanes are among the most affected components [72].

In Refs. [62,68], examples of novel multiscale thermoplastic polymer composites are discussed for use in self-lubricating bearings. They were developed by the addition of macro- and micro-reinforcements (short carbon fiber (SCF), GF, and CF, carbon-based nanofillers (nanodiamonds (ND) and carbon nanotubes (CNTs)), and 2D materials (graphene oxide (GO), molybdenum disulfide (MoS_2)) to polymers, resulting in better properties (mechanical and tribological) through a synergistic effect obtained via the multiscale mode. This reduces the need for “oil-jacking” (when high-pressure oil is injected into the gap between the bearing and counterface during start-up to separate the surfaces until a self-sustaining film can be formed) [73]. Thermoplastic polymer composites combat friction and wear issues owing to their extreme contact pressure during operation (~ 30 MPa) and longevity of operation (~ 40 years) [62]. The ultra-high-molecular-weight polyethylene multiscale composite with GO, ND, and SCF provided a significant reduction in friction and wear compared to pure ultra-high molecular weight polyethylene under water-lubricated conditions, whereas polytetra fluoroethylene (PTFE) reinforced with GF and MoS_2 exhibited a lower wear rate with respect to unfilled PTFE [62].

US Synthetic is developing a novel polycrystalline diamond (PCD) bearing shaft for the RivGen Power System in a hydrokinetic context to deliver electricity to existing remote community grids [6]. Researchers at the University of Alaska, USA compared four bearing/bushing materials under a load of freshwater for 60 h, and wear (mm) measurements were performed. Fig. 4 [74] shows the benefits of the PCD bearing material compared to Vesconite™ (self-lubricated thermoplastic), a Columbia Industrial Products (CIP) marine composite with solid lubricant†, and Feroform™ (composites with PTFE) materials. The test compared wear on the far, center, and drive-side of the bearing/bushing. Through the use of PCD bearing technology in its RivGen Power System (Fig. 5), the following benefits were achieved:

- A process fluid-cooled bearing-shaft assembly that: ① completely eliminated seals, ② reduced excess component weight, and ③ removed the need for contaminating lubricants and ongoing maintenance.
- A diamond material that easily resists abrasive particles and the sediment flowing in water.
- A sliding-element bearing surface that: ① handles higher loads, ② minimizes operational wear, and ③ delivers a lower friction coefficient (0.01).

† This material is a medium-weave PTFE and polyester fabric blend. The addition of solid lubricants to the resin reduces friction, extends wear life, and improves performance in wet and dry applications (<https://www.hydroreview.com/world-regions/bearings-and-seals-applying-the-latest-technologies/#gref>).

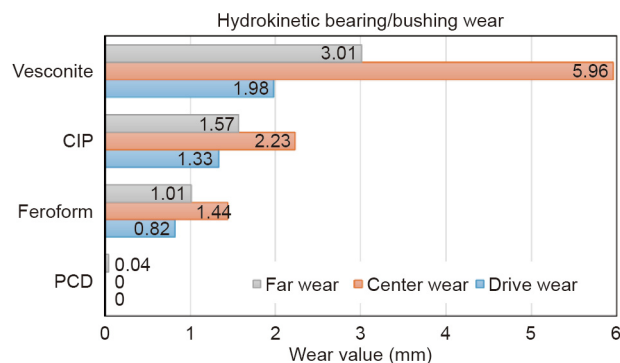


Fig. 4. Experimental study of abrasion characteristics for critical sliding components for use in hydrokinetic devices, wear test (mm) under load over 60 h [74].

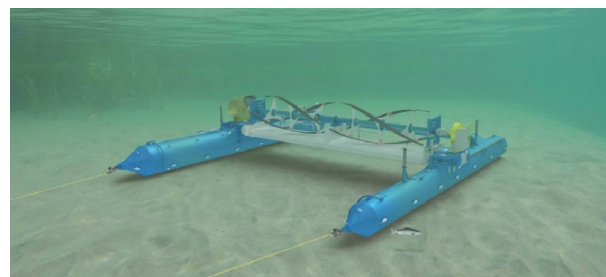


Fig. 5. RivGen Power System in a hydrokinetic context (photo courtesy of Susy Kist, Ocean Renewable Power Company (ORPC), USA).

5. Novel materials for sealing

A sealing interconnects component, minimizes water leakage, and protects against the intrusion of water and dirt. The sealing of the main shaft of a turbine is the major challenge. Ideally, the sealing process should be complete; however, owing to the high costs, the primary aim of shaft sealing is limited to controlling leakage to an acceptable amount. In Ref. [75], hydropower sealing techniques were discussed.

The first hydraulic turbine used compression packing to seal the turbine shaft. However, early packing requires a significant amount of water for cooling. As compression packing devices have evolved, novel materials, lubricants, and blocking agents have been developed to extend the packing life by reducing the amount of cooling water. Several technologies have been developed over the years, including carbon-segmented rings and elastomeric radial sealing elements [75,76]. Mechanical sealing of axial faces is becoming popular as a viable long-term sealing solution for hydraulic turbines.

Soft carbon graphite is commonly used as a sealing face and is paired with a hard-facing material (e.g., alumina ceramic). However, the thermal capabilities and pressure–velocity (PV) performance of the alumina ceramic, which acts as a very good insulator, are poor. The PV performance is evaluated by multiplying the pressure at the sealing interface by the rotational velocity of the mean face diameter of the mechanical seal. When the PV value exceeds the limit placed on the sealing face pair, the life span is reduced owing to the high wear and heat generation [76]. To overcome the PV limit, novel materials, such as SiC, have been developed, which improves the PV performance by 2–3 times, generates 60% less heat, and reduces the required cooling water. Furthermore, SiC has a very good abrasion resistance, which is a useful property for erosive waters. When compared to the carbon/ceramic face pair, a SiC/SiC face pair has a PV limit of 33%

higher while generating 50% less heat [76]. The development of high-performance thermoplastic sealing materials and elastic polymers are also underway, that exhibit as much as five times the wear and abrasion resistance of traditional rubber elastomers [75]. Additional case studies on bearings and sealing can be found in Refs. [77,78].

6. Novel materials for ocean hydropower and hydrokinetic turbines

Hydropower plants in ocean contexts convert the energy of tidal flows and waves into electricity. In the tidal context, low-head turbines exploit the potential energy of tidal ranges, whereas hydrokinetic turbines exploit the kinetic energy of tidal flows and ocean currents. In the wave energy context, hydromechanical devices convert the oscillatory motion of waves into mechanical energy [79,80].

The ocean climate is particularly severe and variable, and seawater is corrosive. Tidal energy converters also undergo fatigue loading, whereas maintenance events have to be rare because access to submerged installations in high-energy locations is challenging. Consequently, and because local loading events such as turbulence and wave-current interactions are not yet well characterized [81], rotors tend to be overdesigned, by up to 30% in some cases, to ensure the required durability. This is inefficient in terms of material usage, cost, and performance. Therefore, novel materials with improved strength, fatigue, and anti-corrosion properties are being developed to reduce costs and increase durability. Most of the prototypes developed to date are fiber composites, such as GFs and CFs, impregnated with an epoxy resin matrix. These novel materials are mainly applicable and economical, owing to their very low rotation speed compared to hydro high-head turbines such as Francis and Pelton turbines. Epoxies are generally selected for underwater applications because, among the thermoset resin systems available, when the chemistry is optimized, they offer excellent resistance to progressive moisture absorption and hydrolytic degradation [82]. Vinyl ester resins and thermoplastic polymers were also considered. The latter provides a potential for recycling; however, it requires alternative manufacturing processes with an additional cost [83]. Table 1 compares traditional materials with composite materials in the ocean hydropower context [84].

A range of material options exist; however, the combination of mechanical performance and durability with the ease of the manufacture of complex shapes has led to the vast majority of developers choosing fiber composites, mostly with CF reinforcements for improved fatigue resistance.

The published information available from prototype tests is quite limited, as these are generally commercial developments. At the time of writing, only one tidal turbine installation can be considered as a commercial farm, the MeyGen project in the Pentland Firth [85]. Some examples of tidal flow energy converter prototypes, in the form of hydrokinetic turbines, are as follows [37,48].

- The SeaFlow project, a 300 kW-tidal prototype, was one of the first sea trials installed off the Devon coast in June 2003. The runner diameter was 11 m, with two composite blades

equipped with strain gauges. The construction involved a central 65 mm thick carbon composite spar covered by stiffened glass/epoxy fairings. A 1.2 MW-twin turbine was immersed in 2008 using a design similar to that of the SeaFlow (SeaGen project). The blades were 7.5 m long.

- In 2003, a tidal power station was installed near Hammerfest (Norway), and the 10 m long blades were made of GF composite.
- In the United States, within the RITE project, six turbines were installed in 2007 in New York. The turbines had a diameter of 4.9 m with three composite blades, similar to existing wind turbine designs. However, some blade failures occurred, and the blades were redesigned.
- The Sabella project comprised the prototype installation off the Brittany coast in April 2008, known as D03. A 500 kW turbine demonstrator (D10) was installed near Ushant Island in 2015. This has six carbon/epoxy blades made of a central prepreg composite spar with infused composite facings. A glass-reinforced composite was used as the generator cover (Fig. 6).
- A 500 kW prototype with blades of 6 m was immersed in Tidal Generation Limited, Denmark, in 2009. It has composite (carbon and glass) blades.
- GF composite tidal turbine blades were used in the OpenHydro turbine, an 11 m-diameter structure. Composites are also of interest for shrouds, mounting frames, and other components of these systems.
- The CRIMSON project, valued at 3.9 million EUR made by Ocean Renewable Power Company (ORPC), USA, was made with foils made entirely of recycled CF, reducing capital and operating expenditures by 33% and 66%, respectively.
- The MeyGen project involves four 1.5 MW turbines with composite blades, three from Andritz Hydro Hammerfest and one from Atlantis (AR1500). The first turbine became operational in 2016, and by 2017, all four turbines were installed. The lease allows up to 400 MW to be installed in different phases of the 25-year project. By January 2020, the MeyGen tidal stream array generated over 25.5 GW-h of electricity.

Composites are also being considered for some wave energy devices; however, they are less commercially advanced than their tidal counterparts. Some examples are as follows.

- A composite structure design of a full-scale Wave Dragon wave energy converter device (the 20 kW prototype was made of steel, Denmark).
- A Kevlar™ and rubber composite is used in the Archimedes wave swing system from AWS Ocean Energy, UK. This exploits submerged buoy-like elements that respond to waves passing above the sea surface by changing their volume in line with



Fig. 6. Sabella D10 tidal turbine dockside in Brest, before installation (photo courtesy of Erwann Nicolas (Sabella, France)).

Table 1
Material properties for tidal turbines, based on Ref. [84].

Material	Density (g·cm ⁻³)	Elastic modulus (GPa)	Tensile strength (MPa)
Carbon steel	7.85	207	400–500
Stainless steel	7.75	193	750–850
Ti alloys	4.50	114	1170
Al alloys	2.70	70	300–550
GF composite	2.10	45	1020
CF composite	1.60	145	1240

the resulting pressure changes, thus floating higher or lower. The induced vertical motion is converted into electric power.

Polymer composites and sandwich materials (composite facings on foam cores) are popular for many floating energy converters where buoyancy is critical.

A considerable experience of composites in seawater from over 50 years of small boat construction exists, and extensive knowledge of fatigue of composites from the wind industry, where composites are the first choice. However, very little experience exists of what happens when composites are subjected to seawater and fatigue loading simultaneously, which is the case for hydropower applications; therefore, this is an area of research [86]. Nevertheless, if CF composites are correctly chosen and manufactured, their long-term durability is excellent [87]. A detailed study on the durability of GF-reinforced epoxy materials in seawater was conducted in Ref. [82]. Three grades of GFs were studied. The residual failure stresses owing to bending decreased when the water absorption increased, especially for composite materials reinforced with E-GF[†], whereas the axial modulus remained unchanged. High-performance glass fibers are also available (e.g., “Advantex”) and confer improved long-term property retention compared to standard E-glass fibers. A similar aging study on carbon/epoxy showed a small reduction in properties after full water saturation through aging at 60 °C. However, it was shown that the thick composites used in tidal turbine blades are unlikely to fully saturate under real operating conditions [88]; therefore, predictions based on full water saturation can be very conservative.

The changes in the properties of carbon/epoxy composites after seawater immersion are governed by the matrix, fiber/matrix interface, and manufacturing quality. This can make material selection more difficult than for metallic materials and requires rigorous quality control procedures; however, the long-term properties can be excellent. An ongoing aging study on Sabella materials, which includes immersion of specimens at different temperatures for over seven years, now indicates a predicted lifetime of well over 20 years [89].

Further advances in the ocean energy sector are related to seawater pumped storage systems, comprising two interconnected reservoirs, where the lower one is the ocean. The plant operates in turbine mode during peak energy demand periods, and in pumping mode during periods of low energy demand to consume the surplus of energy generated by solar and wind power plants. The corrosion problems could be solved using GF-reinforced plastic pipes and corrosion-resistant steel for turbines and parts in contact with water. Novel materials have been introduced, for example, ethylene propylene diene monomer (EPDM) rubber sheet has been adopted for the lining of the upper reservoir. The EPDM has been proven via several tests to exhibit excellent material properties and weather-resistant characteristics [90]. A novel fluid with a density of 2.5 times higher than the water fluid was introduced in 2017 by RheEnergise, UK, called R19 fluid, which is inert and non-reactive, conceived to be used in closed-loop pumped hydro plants. Approximately 65% of pumped energy storage project costs are civil engineering-related, making projects 2.5 times smaller, thus offering huge saving opportunities.

7. Discussion

Hydropower is a clean renewable energy source and, compared to other renewable sources, hydropower equipment does not con-

tain critical materials such as lithium and cobalt (used in electric vehicles), neodymium, praseodymium, and dysprosium (used in electric vehicles and wind power) [91]. Several novel materials are being introduced in the hydropower sector, and many ongoing studies are being conducted [92]. Novel materials can find applications in both new power plants and refurbishment projects [93].

The introduction of novel materials can provide increased efficiency, both in reaction turbines and free surface turbines (e.g., the vortex turbine, Archimedes screw, and water wheels), as well as a reduction in weight and extension of the lifespan. However, the reduction in the weight of turbine runners would lead to a reduction in the spinning reserve, which guarantees hydropower flexibility. Some hydraulic machines have been combined previously, even with flywheels, to increase the spinning reserve, which is relevant for frequency control [94]. Superhydrophobic-coated materials can improve efficiency, and organic-coated triboelectric nanogenerators are expected to be used in the ocean hydropower sector. The development of fiber-reinforced composite materials, which are already widespread in marine and wind energy sectors, but recently introduced in hydropower turbines, are underway, particularly CF composites. Interest in other lightweight materials, including polymers, such as high-density polyethylene, in the water wheel sector, exists. These materials ensure higher efficiency, low weight, and higher resistance in severe environments. The case studies presented here confirm that weight reduction (50% to 70% for reaction turbines, 50% for vortex turbines, and 30% for water wheels) can increase efficiency and reduce costs. However, degradation owing to the coupling between the CF composites and metals may pose a problem in a wet environment; if electrical coupling occurs between the CFs and the metal, galvanic corrosion may occur. This is a well-known phenomenon that has received considerable attention over the last 30 years [95]; however, it still needs to be considered during design.

Novel materials for dams have also been developed, such as cemented rockfill and cemented soil, CF, and GF materials. They increase the lifespan of the structure, reduce deformation, and simplify the installation process. The cemented rockfill material has a higher modulus than the rockfill material, which can improve the mechanical response. Cemented rockfill or soil dams are advantageous over rockfill embankment dams with higher material erosion resistance, which allows overtopping with low failure risk during extreme floods. The covering of the dam surface with bituminous conglomerate is another trend that is being developed to simplify waterproofing.

In the bearing assembly sector, PCD bearings and PTFE have been introduced to improve performance and reduce oil need, thus increasing the environmental sustainability of the plant and almost eliminating wear. SiC has been applied in seals, improving their PV performance by 2–3 times and generating 60% less heat, reducing the cooling water required for the sealing faces, and abrasion and erosion wear. Lubrication made with water and vegetable oil is the main strategy for reducing oil-related pollution.

Advanced composite materials, such as GF and CF-reinforced polymers, can reduce costs and increase durability in ocean conditions, and study cases have already been discussed in the literature, with specific applications on hydrokinetic devices. The current EU H2020 project RealTide [96] is focused on the improvement of the reliability of tidal turbines, with an emphasis on the improvement of the understanding of composite blade materials. The durability of alternative composites based on basalt or natural fiber reinforcement is also being examined to develop materials with lower environmental impact [57,97]. Although their mechanical properties are not as good as those of CFs, the use of these materials may be justified by life cycle analysis. Alternative

[†] E-GFs were originally developed for electrical insulation applications (that is the origin of the “E”). E-GFs are, by many orders of magnitude, the most widely used of all fibrous reinforcements, owing to their low cost and early development compared to other fibers.

biosourced and biodegradable polymer matrix materials have also received attention [98].

In Ref. [99], the need to determine the mechanical properties and rheological behavior of various membrane materials for applications in the embedment of steel spiral cases in concrete is also highlighted. Polyurethane (PU) cork materials are increasingly being used to replace polymer foams in Chinese hydroelectric power plants. New cavitation-resistant materials should also be tested and further investigated. For example, non-strain-rate-sensitive materials with a higher number of slip systems and greater ability to undergo plastic deformation, such as Co and austenitic stainless steel. Recent studies have shown that tungsten carbide-based composites, such as 86WC–10Co–4Cr, have much-improved resistance against sediment erosion [100], whereas HVOF and plasma spraying techniques provide a promising solution for slurry erosion. Ni–Cr- and WC-based coatings and other materials, such as NiAl intermetallic compounds, exhibit high resistance to slurry erosion. Variants of WC–Co–Cr have been investigated; hence, a need to further study the performance of various composite combinations using HVOF and plasma spraying techniques exists [23]. Studies are also being conducted on novel cold spray processes aimed at the rapid repair of turbine blades after cavitation damage [22].

The installation of floating photovoltaic panels on the reservoir or dam surface is an emerging trend [101]; thus, innovations in the photovoltaic sector will be beneficial in the hydropower sector [102].

Based on the results obtained in Ref. [37], future research should be devoted to obtaining novel composite architectures, such as fabric-reinforced compounds. Reinforced compounds need to be more resistant, rigid, and adapted to withstand impacts than compounds reinforced with unidirectional fiber layers, which are prone to delamination. Examples are the 3D pinned and tufted materials that are being developed for the aerospace and automotive industries. These use through-thickness reinforcement and compensate for reduced in-plane properties with significant improvements in out-of-plane and impact behavior [32]. Consequently, theories for numerical simulations must be reformulated and generalized to fit these novel materials. This, along with the large deformations, the incorporation of the misalignment of the fibers, and the presence of manufacturing defects, will allow a more realistic consideration of the interactions between orthogonal fibers located both in the same plane and out-of-plane, providing a basis for improved numerical simulation of the fabric-reinforced composites.

It is worth noting that in the optimal material selection for hydropower, many factors including mechanical, electrical, and physical properties (e.g., corrosion resistance) and economic and environmental considerations must be considered, such that multiple attribute decision-making strategies are essential [103]. Finally, with the breakthrough of supra-conducting materials, future developments are expected. High-capacity laser beam techniques for underground excavation will allow quick, safe, and cheap excavation of underground structures such as tunnels and caves [104].

8. Conclusions

Hydropower is a sector where the development of novel technologies is underway to improve its sustainability and flexibility, and novel materials can play a central role in improving efficiency, resistance, reliability, extending lifespan, and making the fabrication, installation, and transport process easier. For example, it is worth noting that: ① Novel materials for turbines include superhydrophobic coatings and superhydrophobic lubricant-infused composites, coatings with triboelectric properties, bimodal coat-

ings with both nanometric and micrometric WC grains, coatings 13Cr4Ni steel, Ni–Al₂O₃, and HVOF-sprayed WC coatings (e.g., Ref. [105]); however, fiber-reinforced polymers including Kevlar™ 49, HDPE, and carbon steel are limited to low-speed applications. ② Novel materials for dams and hydraulic structures include GF-reinforced concrete, rock-bolted underpinning system, rock-filled concrete-cemented, and bituminous conglomerate. Significant development of geo-membrane placement on the upstream faces of concrete dams to reduce leakage and mitigate concrete expansion has been made [106]. Novel materials for waterways include high tensile strength steel pipes and superhydrophilic surfaces to reduce friction losses. ③ The development of novel PCD, thermoplastic polymers (e.g., PTFE), and soft carbon graphite for bearings, and vegetable or water-based oils instead of common oil lubricants are underway, although more expensive [107]. ④ In the ocean context, epoxies, and composite materials, and EPDM rubber for lining the reservoir of pumped hydropower plants are under consideration.

However, the implementation of some of these materials is limited by their high cost with respect to traditional materials, and experience with novel materials such as composites is still limited; the long-term behavior over 100 years is yet unknown. For example, the weight of a fish ladder made of composite material was found 14.2% lower than the equivalent concrete structure, but the total material cost (excluding installation costs) was five times higher with respect to a concrete ladder of the same size [108]. Nevertheless, the price of CF has gradually reduced in recent years and is currently approximately ten times the cost of stainless steel. In the case of the weight savings from low densities of composites and the fill ratio of CF, the total material costs of hydro turbines using these two types of materials are becoming increasingly similar.

The development of a hydropower component using a completely novel material is a complex design effort. This requires the investigation of its durability (e.g., aging under high mechanical loads, wet aging, resistance to cavitation, and fatigue) or mechanical properties, as well as costs, weight, and environmental sustainability, to better understand the life benefits and limitations. Novel materials should also contribute to reducing CO₂ emissions. Future research should be devoted to obtaining new composite architectures, such as 3D reinforced compounds. To promote the development of tidal turbines, further work is required on the corrosion protection system for the remaining metallic components (e.g., with novel graphene-based coatings). More information on the performance of these corrosion protection systems and their life cycle assessment should be collected in future research. Bearing eco-friendly tribology is another emerging research sector for improving sustainability.

Acknowledgments

We thank the US Synthetic for sharing its information about the diamond bearings and Helmut Mitterfellner for sharing information about the carbon steel water wheel. We thank Susy Kist (ORPC) and Erwann Nicolas (Sabella) for the photo courtesy, and Maria Vittoria Vignoli of Cooperativa Edile Appennino for the information on bituminous membranes.

Compliance with ethical guidelines

Emanuele Quaranta and Peter Davies declare that they have no conflicts of interest or financial conflicts to disclose.

References

- [1] International Hydropower Association. 2020 hydropower status report sector trends and insights. Report. London: IHA Central Office; 2020.

- [2] Kougiaris I, Aggidis G, Avellan F, Deniz S, Lundin U, Moro A, et al. Analysis of emerging technologies in the hydropower sector. *Renew Sustain Energy Rev* 2019;113:109257.
- [3] Frey GW, Linke DM. Hydropower as a renewable and sustainable energy resource meeting global energy challenges in a reasonable way. *Energy Policy* 2002;30(14):1261–5.
- [4] Moran EF, Lopez MC, Moore N, Müller N, Hyndman DW. Sustainable hydropower in the 21st century. *Proc Natl Acad Sci USA* 2018;115(47):11891–8.
- [5] Acreman MC, Ferguson AJD. Environmental flows and the European water framework directive. *Freshw Biol* 2010;55(1):32–48.
- [6] Quaranta E, Bonjean M, Cuvato D, Sarma P, Slachmuylers G, Clementi R, et al. Hydropower case study collection: innovative low head and ecologically improved turbines, hydropower in existing infrastructures, hydropeaking reduction, digitalization and governing systems. *Sustainability* 2020;12:8873.
- [7] Li H, Zhou D, Martinez JJ, Deng ZD, Johnson KI, Westman MP. Design and performance of composite runner blades for ultra low head turbines. *Renew Energy* 2019;132:1280–9.
- [8] Quaranta E, Revelli R. Gravity water wheels as a micro hydropower energy source: a review based on historic data, design methods, efficiencies and modern optimizations. *Renew Sustain Energy Rev* 2018;97:414–27.
- [9] Tong C. Introduction to materials for advanced energy systems. Cham: Springer International Publishing; 2019.
- [10] Quaranta E. Estimation of the permanent weight load of water wheels for civil engineering and hydropower applications and dataset collection. *Sustain Energy Technol Assess* 2020;40:1–8.
- [11] Muñoz AH, Chiang LE, De la Jara EA. A design tool and fabrication guidelines for small low cost horizontal axis hydrokinetic turbines. *Energy Sustain Dev* 2014;22:21–33.
- [12] Sritram P, Treedet W, Suntivarakorn R. Effect of turbine materials on power generation efficiency from free water vortex hydro power plant. In: Proceedings of the 4th Global Conference on Materials Science and Engineering (CMSE 2015); 2015 Aug 3–6; Macao, China. London: IOPscience; 2015.
- [13] Kumar R, Singal SK. Operation and maintenance problems in hydro turbine material in small hydro power plant. *Mater Today Proc* 2015;2:2323–31.
- [14] Ravens T, Ali M. Abrasion testing of critical components of hydrokinetic devices. Final report. Washington, DC: US Department of Energy; 2013 Dec. Report No.: DE-EE0003631.
- [15] Jiang X, Overman N, Canfield N, Ross K. Friction stir processing of dual certified 304/304L austenitic stainless steel for improved cavitation erosion resistance. *Appl Surf Sci* 2019;471:387–93.
- [16] Whitehead M, Albertani R. How composite materials can be used for small hydro turbines. *Hydro Rev* 2015;34(2):56–63.
- [17] Lee JY, An J, Chua CK. Fundamentals and applications of 3D printing for novel materials. *Appl Mater Today* 2017;7:120–33.
- [18] Darmanin T, Guittard F. Superhydrophobic and superoleophobic properties in nature. *Mater Today* 2015;18(5):273–85.
- [19] Shirtcliffe NJ, McHale G, Atherton S, Newton MI. An introduction to superhydrophobicity. *Adv Colloid Interface Sci* 2010;161(1–2):124–38.
- [20] Haghghi MHS, Mirghavami SM, Ghorani MM, Riasi A, Chini SF. A numerical study on the performance of a superhydrophobic coated very low head (VLH) axial hydraulic turbine using entropy generation method. *Renew Energy* 2020;147:409–22.
- [21] Rico V, Mora J, García P, Agüero A, Borrás A, González-Elipe AR, et al. Robust anti-icing superhydrophobic aluminum alloy surfaces by grafting fluorocarbon molecular chains. *Appl Mater Today* 2020;21:100815.
- [22] Materials science for hydropower-providing innovative technologies to improve hydropower performance [Internet]. Washington, DC: Pacific Northwest National Laboratory; [cited 2021 Oct 28]. Available from: <https://www.pnnl.gov/materials-science-hydropower>.
- [23] Prashar G, Vasudev H, Thakur L. Performance of different coating materials against slurry erosion failure in hydrodynamic turbines: a review. *Eng Fail Anal* 2020;115:104622.
- [24] Roa CV, Valdes JA, Larrahondo F, Rodríguez SA, Coronado JJ. Comparison of the resistance to cavitation erosion and slurry erosion of four kinds of surface modification on 13–4 CA6NM hydro-machinery steel. *J Mater Eng Perform* 2021;6:1–18.
- [25] Fan FR, Tian ZQ, Wang ZL. Flexible triboelectric generator. *Nano Energy* 2012;1(2):328–34.
- [26] Wang B, Wu Y, Liu Y, Zheng Y, Liu Y, Xu C, et al. New hydrophobic organic coating based triboelectric nanogenerator for efficient and stable hydropower harvesting. *ACS Appl Mater Interfaces* 2020;12(28):31351–9.
- [27] Wang ZL, Wang AC. On the origin of contact-electrification. *Mater Today* 2019;30:34–51.
- [28] Jiang D, Guo F, Xu M, Cai J, Cong S, Jia M, et al. Conformal fluorine coated carbon paper for an energy harvesting water wheel. *Nano Energy* 2019;58:842–51.
- [29] Singh P, Singh S, Vardhan S, Patnaik A. Sustainability of maintenance management practices in hydropower plant: a conceptual framework. *Mater Today Proc* 2020;28(3):1659–74.
- [30] Khabirul Islam AKM, Bhuyan S, Chowdhury FA. Advanced composite Pelton wheel design and study its performance for pico/micro hydro power plant application. *Eng Innovative Technol* 2013;2(11):126–32.
- [31] Weber AZ. How cells for energy storage. Workshop summary report. In: Proceedings of 2012 Flow Cell Workshop. 2012 Mar 7–8; Washington, DC, USA. Washington, DC: US Department of Energy; 2012.
- [32] Mouritz AP. Mechanics of 3D fiber reinforced polymer composites. In: Altenbach H, Öchsner A, editors. *Encyclopedia of continuum mechanics*. Berlin: Springer; 2020.
- [33] Das S, Warren J, West D, Schexnayder SM. Global carbon fiber composites supply chain competitiveness analysis. Technical report. Washington, DC: USDOE Office of Energy Efficiency and Renewable Energy; 2016. Report No.: NREL/TP-650-66071. Contract No.: DE-AC36-08GO28308.
- [34] Davies P, Rajapakse YDS, editors. *Durability of composites in a marine environment*. Dordrecht: Springer; 2014.
- [35] Davies P, Rajapakse YDS, editors. *Durability of composites in a marine environment 2*. Dordrecht: Springer; 2018.
- [36] Kang TJ, Kim C. Energy-absorption mechanisms in Kevlar multiaxial warp-knit fabric composites under impact loading. *Compos Sci Technol* 2000;60:773–84.
- [37] Aramayo SAO, Nallim LG, Oller S, Martínez X. A river bed hydrokinetic turbine: a laminated composite material rotor design. Barcelona: International Center for Numerical Methods in Engineering; 2017.
- [38] Wikander Ö. *Handbook of ancient water technology*. Brill: Leiden; 2000.
- [39] Güllüoğlu AMM, Bendeş O, Yılmaz B, Yildiz A. Investigation of manufacturing of a Pelton turbine runner of composite material on a 3D printer. *Gazi Univ J Sci Part A Eng Innovation* 2021;8(1):24–34.
- [40] Quaranta E, Revelli R. Performance optimization of overshot water wheels at high rotational speeds for hydropower applications. *J Hydraul Eng* 2020;146(9):06020011.
- [41] Dutta AK, Shrestha B, Shahi J, Chaudhary VK, Shrestha PL. Re-design and optimization of traditional undershot wheel using high density polyethylene (HDPE) blades. In: Proceedings of the International Symposium on Current Research in Hydraulic Turbines; 2016 Mar 14; Dhulikhel, Nepal. Kathmandu: Kathmandu University; 2016.
- [42] Quaranta E. Stream water wheels as renewable energy supply in flowing water: theoretical considerations, performance assessment and design recommendations. *Energy Sustain Dev* 2018;45:96–109.
- [43] Straalsund JL, Harding SF, Nuernbergk DM, Rorres C. Experimental evaluation of advanced Archimedes hydrodynamic screw geometries. *J Hydraul Eng* 2018;144(8):04018052.
- [44] Marsh G. Wave and tidal power—an emerging new market for composites. *Reinf Plast* 2009;53(5):20–4.
- [45] Yaseen ZM, Ameen AMS, Aldlemy MS, Ali M, Abdulmohsin Afan H, Zhu S, et al. State-of-the-art-powerhouse, dam structure, and turbine operation and vibrations. *Sustainability* 2020;12(4):1676.
- [46] Schleiss A, Pougatsch H. *Les barrages—Du projet à la mise en service*. Lausanne: EPFL Press; 2020. French.
- [47] Baeza FJ, Galao O, Zornoza E, Garcés P. Multifunctional cement composites strain and damage sensors applied on reinforced concrete (RC) structural elements. *Materials* 2013;6(3):841–55.
- [48] Peng Y, Hu C, Chen R. Study on cemented-rockfill dam in hydropower station construction. In: Proceedings of the 2010 Asia-Pacific Power and Energy Engineering Conference; 2010 Mar 28–31; Chengdu, China. New York: IEEE; 2010.
- [49] Chen SH, Yang ZM, Wang WM, Shahrour I. Study on rock bolt reinforcement for a gravity dam foundation. *Rock Mech Rock Eng* 2012;45:75–87.
- [50] Hellgren R, Malm R, Ansell A. Progressive failure analysis of a concrete dam anchored with passive rock bolts. *Infrastructures* 2020;5(3):28.
- [51] Kodymov J, Thomas A, Will M. Life cycle analysis of rock bolts. *Adv Tunneling Tech* 2017:47–9.
- [52] Jin F, Zhou H, Huang D. Research on rock-filled concrete dams: a review. *Dam Eng* 2018;29:101–12.
- [53] Jia J, Lino M, Jin F, Zheng C. The cemented material dam: a new, environmentally friendly type of dam. *Engineering* 2016;2(4):490–7.
- [54] Aniskin N, Trong CN. The thermal stress of roller-compacted concrete dams during construction. *MATEC Web Conf* 2018;196:04059.
- [55] Mafra JMQ, Mello J, Eldridge T, Breul B. Two case histories of dams waterproofing with bituminous geomembrane. Proceedings of the First Pan American Geosynthetics Conference & Exhibition; 2008 Mar 2–5. Cancun, Mexico. Austin: International Geosynthetics Society; 2008.
- [56] Marchi M, Vignoli MV, Picariello F. La nuova tecnica di impermeabilizzazione con membrane bituminose. *Strade e Autostrade* 2017;1:98–101. Italian.
- [57] Verpoest I. Flax and hemp fiber composites: a market reality. Paris: JEC Publications; 2018.
- [58] Lee JW, Park CG, Kim JO, Lee SK, Kim PS. Durability characteristics of glass fiber reinforced polymer composite cladding plates for application of rubber dam. *J Korean Soc Agric Eng* 2011;53(5):17–23.
- [59] Nogueira HIS, Pfister M, Schleiss AJ. Approaches to reduce friction losses in headrace waterways of hydropower plants. *J Hydraul Eng* 2016;142(5):02516001.
- [60] Aoki K, Minami M. Construction of steel penstocks using HT100 at Kannagawa Hydropower Plant. In: Horikawa K, editor. Proceedings of the Conference on High Strength Steels for Hydropower Plants; 2009 Jul 20–22; Takasaki, Japan. Tokyo: Japan Electric Power Civil Engineering Association; 2009.
- [61] Hachem FE, Schleiss AJ. The design of steel-lined pressure tunnels and shafts. *Int J Hydropower Dams* 2009;16(3):142–51.
- [62] Saravanan P, Emami N. Sustainable tribology: processing and characterization of multiscale thermoplastic composites within hydropower applications. In: Sanjay MR, Siengchin S, Parameswarapillai J, Friedrich K,

- editors. *Tribology of polymer composites*. Amsterdam: Elsevier. p. 241–77.
- [63] Ganjoo Haghighi H. Guide vane bearings and guide vane seals of pump turbine [dissertation]. Vienna: Vienna University of Technology; 2011.
- [64] St-Germain F. Addressing pressure loss and oil leakage in Kaplan Bulb turbines and the impact on efficiency [Internet]. 2018 Dec 12 [cited 2021 Oct 28]. BBA blog; Available online: <https://www.bba.ca/publication/addressing-pressure-loss-issues-for-the-kaplan-turbine-runner-blade-and-impact-on-efficiency/>.
- [65] Sasaki S. Environmentally friendly tribology (Eco-tribology). *J Mech Sci Technol* 2010;24(1):67–71.
- [66] Smith S, Ort T. Utilization of environmentally acceptable lubricants. *Voith Hydro*.
- [67] Wenke S. Changing your risk profile with vegetable oil. *Hydro Rev* 2017;36(5):50–5.
- [68] Somberg J, Saravanan P, Shankar Vadivel H, Berglund K, Shi Y, Ukonsaari J, et al. Tribological characterisation of polymer composites for hydropower bearings: experimentally developed versus commercial materials. *Tribol Int* 2021;162:107101.
- [69] Ingram EA, Ray WR. Bearings & seals: examples of innovations and good ideas. *Power Eng* 2010;114(9):50–5.
- [70] Oguma T, Nakagawa N, Mikami M, Thantrong L, Kizaki Y, Takimoto F. Water lubricated guide bearing with self-aligning segments. *Int J Fluid Mach Syst* 2013;6(2):49–55.
- [71] Jones JA, Palylyk RA, Willis P, Weber RA. Greaseless bushings for hydropower applications: program, testing, and results. Technical Report. Champaign: Construction Engineering Research Lab (Army); 1999.
- [72] Rodiouchkina M, Berglund K, Mouzon J, Forsberg F, Ullah Shah F, Rodushkin I, et al. Material characterization and influence of sliding speed and pressure on friction and wear behavior of self-lubricating bearing materials for hydropower applications. *Lubricants* 2018;6(2):39.
- [73] McCarthy D. Sliding bearings for hydropower applications: novel materials, surface texture and EALs [dissertation]. Luleå: Luleå tekniska University; 2008.
- [74] Bromaghin A, Ali M, Ravens T, Petersen T, Hoffman J. Experimental study of abrasion characteristics for critical sliding components for use in hydrokinetic devices. *Renew Energy* 2014;66:205–14.
- [75] Ren G, Oge K. Hydro-turbine main shaft axial seals of elastic polymer-principle and practice. In: *Proceedings of Waterpower XVI Conference*; 2009 Jul 27–30; Spokane, WA, USA. Tulsa: Pennwell Corporation; 2009.
- [76] Evans WA, Sousa J. Advances in sealing systems for water turbines. *Hydro Rev* 2014;5(22):20222426.
- [77] Ingram E. Bearings and seals: applying the latest technologies. *Hydro Rev* 2011;30(4):22–36.
- [78] Proven designs and the next generation-turbine seals [Internet]. Pointe-Claire: Fugesco Inc.; 2021 [cited 2021 Oct 28]. Available online: https://www.fugesco.com/upload/blocchi/X168allegatoALLEGATO_DOWNLOAD1-2X_Hydropower_EN_WEB.pdf.
- [79] Waters S, Aggidis G. Tidal range technologies and state of the art in review. *Renew Sustain Energy Rev* 2016;59:514–29.
- [80] Calvário M, Sutherland LS, Guedes Soares C. A review of the applications of composite materials in wave and tidal energy devices. In: *Proceedings of the 17th International Congress of the International Maritime Association of the Mediterranean (IMAM 2017)*; 2017 Oct 9–11; Lisbon, Portugal. Los Angeles: CRC Press; 2017.
- [81] Wang SQ, Zhang Y, Xie YY, Xu G, Liu K, Zheng Y. Hydrodynamic analysis of horizontal axis tidal current turbine under the wave-current condition. *J Mar Sci Eng* 2020;8(8):562.
- [82] Boisseau A, Davies P, Thiebaud F. Sea water ageing of composites for ocean conversion systems: influence of glass fiber type on static behaviour. *Appl Compos Mater* 2012;19(3–4):459–73.
- [83] Arhant M, Davies P. Thermoplastic matrix composites for marine applications. In: Pemberton R, Summerscales J, Graham-Jones J, editors. *Marine composites: design and performance*. Cambridge: Woodhead; 2019. p. 31–54.
- [84] Shiekh Elsouk MN, Santa Cruz A, Guillou SS. Review on the characterization and selection of the advanced materials for tidal turbine blades. In: *Proceedings of the 7th International Conference on Ocean Energy*; 2018 Jun 12–14; Cherbourg, France. Paris: Ocean Energy Systems; 2018.
- [85] Tidal stream projects-MEYGEN [Internet]. Edinburgh: SIMEC Atlantis Energy; c2021 [cited 2020 Oct 28]. Available from: <https://simecatlantis.com/projects/meygen/>.
- [86] Humeau C, Davies P, Jacquemin F. An experimental study of water diffusion in carbon/epoxy composites under static tensile stress. *Compos Part A Appl Sci Manuf* 2018;107:94–104.
- [87] Alam P, Robert C, Brádaigh CMO. Tidal turbine blade composites—a review on the effects of hygrothermal aging on the properties of CFRP. *Compos Part B Eng* 2018;149(15):248–59.
- [88] Tual N, Carrere N, Davies P, Bonnemains T, Lolive E. Characterization of sea water ageing effects on mechanical properties of carbon/epoxy composites for tidal turbine blades. *Compos Part A Appl Sci Manuf* 2015;78:380–9.
- [89] Davies P. Towards more representative accelerated aging of marine composites. In: Lee SW, editor. *Advances in thick section composite and sandwich structures*. An anthology of ONR-sponsored research. Berlin: Springer; 2020. p. 507–27.
- [90] Katsaprakakis DA, Christakis DG, Stefanakis I, Spanos P, Stefanakis N. Technical details regarding the design, the construction and the operation of seawater pumped storage systems. *Energy* 2013;55:619–30.
- [91] Klimenko VV, Ratner SV, Tereshin AG. Constraints imposed by key-material resources on renewable energy development. *Renew Sustain Energy Rev* 2021;144:111011.
- [92] Robb D. Hydro's fish-friendly turbines. *Renewable Energy Focus* 2011;12(2):16–7.
- [93] Quaranta E, Aggidis G, Boes RM, Comoglio C, De Michele C, Patro ER, et al. Assessing the energy potential of modernizing the European hydropower fleet. *Energy Conversion and Management* 2021;246:114655.
- [94] Forrest K, Tarroja B, Chiang F, AghaKouchak A, Samuelsen S. Assessing climate change impacts on California hydropower generation and ancillary services provision. *Clim Change* 2018;151(3):395–412.
- [95] Alias MN, Brown R. Corrosion behavior of carbon fiber composites in the marine environment. *Corros Sci* 1993;35(1–4):395–402.
- [96] Realtide [Internet]. Edinburgh: The University of Edinburgh; c2021 [cited 2021 Oct 28]. Available from: <https://www.realtide.eu/>.
- [97] Davies P, Verboouwe W. Evaluation of basalt fiber composites for marine applications. *Appl Compos Mater* 2018;25(2):299–308.
- [98] Mukherjee T, Kao N. PLA based biopolymer reinforced with natural fiber: a review. *J Polym Environ* 2011;19:714.
- [99] Zhang QL, Wu HG. Embedment of steel spiral cases in concrete: China's experience. *Renew Sustain Energy Rev* 2017;72:1271–81.
- [100] Dorji U, Ghomashchi R. Hydro turbine failure mechanisms: an overview. *Eng Fail Anal* 2014;44:136–47.
- [101] Lee N, Grunwald U, Rosenlieb E, Mirlletz H, Aznar A, Spencer R, et al. Hybrid floating solar photovoltaics-hydropower systems: benefits and global assessment of technical potential. *Renew Energy* 2020;162:1415–27.
- [102] Choudhary P, Srivastava RK. Sustainability perspectives—a review for solar photovoltaic trends and growth opportunities. *J Clean Prod* 2019;227:589–612.
- [103] Kumar R, Singal SK. Penstock material selection in small hydropower plants using MADM methods. *Renew Sustain Energy Rev* 2015;52:240–55.
- [104] Schleiss AJ. Hydropower in the Swiss Alps in the next century. In: *Proceedings of the Hydropower into the Next Century*; 1999 Oct 18–19; Gmunden, Austria; 1999.
- [105] Felix D. Experimental investigation on suspended sediment, hydro-abrasive erosion and efficiency reductions of coated Pelton turbines [dissertation]. Zurich: ETH Zurich; 2017.
- [106] Scuro A, Vaschetti G. Geomembrane sealing systems for dams: ICOLD Bulletin 135. *Innovative Infrastruct Solutions* 2017;2(1):1–17.
- [107] Gonzalez-Reyes GA, Bayo-Besteiro S, Vich Llobet J, Anel JA. Environmental and economic constraints on the use of lubricant oils for wind and hydropower generation: the case of NATURGY. *Sustainability* 2020;12(10):4242.
- [108] Whitehead M. Design and manufacturing study of hydroelectric turbines using recycled and natural fiber composites [dissertation]. Corvallis: Oregon State University; 2013.